



This open access document is posted as a preprint in the Beilstein Archives at <https://doi.org/10.3762/bxiv.2022.77.v1> and is considered to be an early communication for feedback before peer review. Before citing this document, please check if a final, peer-reviewed version has been published.

This document is not formatted, has not undergone copyediting or typesetting, and may contain errors, unsubstantiated scientific claims or preliminary data.

Preprint Title Induced electric conductivity in organic polymer

Authors Konstantin Y. Arutyunov, Anatoli S. Gurski, Vladimir V. Artemov, Alexander L. Vasiliev, Azat R. Yusupov, Danfis D. Karamov and Alexei N. Lachinov

Publication Date 23 Sep. 2022

Article Type Full Research Paper

ORCID® IDs Konstantin Y. Arutyunov - <https://orcid.org/0000-0001-9373-5185>;
Vladimir V. Artemov - <https://orcid.org/0000-0002-5253-8481>; Danfis D. Karamov - <https://orcid.org/0000-0002-7081-1947>

License and Terms: This document is copyright 2022 the Author(s); licensee Beilstein-Institut.

This is an open access work under the terms of the Creative Commons Attribution License (<https://creativecommons.org/licenses/by/4.0>). Please note that the reuse, redistribution and reproduction in particular requires that the author(s) and source are credited and that individual graphics may be subject to special legal provisions.

The license is subject to the Beilstein Archives terms and conditions: <https://www.beilstein-archives.org/xiv/terms>.

The definitive version of this work can be found at <https://doi.org/10.3762/bxiv.2022.77.v1>

Induced electric conductivity in organic polymer

Konstantin Yu. Arutyunov^{1,2*}, Anatoli S. Gurski¹, Vladimir V. Artemov³, Alexander L. Vasiliev^{3,4}, Azat R. Yusupov⁵, Danfis D. Karamov⁶, Alexei N. Lachinov^{5,6}

Address:

¹ National Research University Higher School of Economics, 101000, Moscow, Russia.

² P. L. Kapitza Institute for Physical Problems RAS, 119334, Moscow, Russia.

³ Federal research center “Crystallography and photonics” RAS, 119333, Moscow, Russia.

⁴ National research center “Kurchatov institute”, 123182, Moscow, Russia.

⁵ Bashkir State Pedagogical University n.a. M. Akmulla, 450008, Ufa, Russia.

⁶ Institute of Molecule and Crystal Physics UFRC RAS, 450054, Ufa, Russia.

Email: karutyunov@hse.ru

* Corresponding author

Abstract

Polydiphenylenephthalide (PDP) belongs to the class of carbocyclic organic electroactive polymers, which exhibit electric conductive properties when an external electric field and/or mechanical stress is applied. In this work, the transport properties of thin-film layered lead–PDP–lead structures were experimentally studied in a wide temperature range. At sufficiently high temperatures, the current voltage characteristics are satisfactorily described in terms of the injection model of currents limited by the space charge. At temperatures below ~8 K, a number of samples exhibit features that can be explained by the effect of induced superconductivity in a thin film of conducting polymer enclosed between two massive superconductors (lead).

Keywords

thin films, conducting polymer, superconductivity

Introduction

Most polymers can be classified as organic dielectrics. However, there exist the specific class of polymers, typically characterized by existence of conjugated p-bonds, which enable delocalization of electrons leading to electric conductivity in the ground state of the system. Relatively recently it was found that finite electric current can pass also through non-conjugated polymers. In the ground state they are wide-band dielectrics, but can exhibit high electric conductivity under the influence of such external parameters as mechanical stress and/or electric field [1]. The effect is interpreted as stimulation of metallic state [2].

Polydiphenylenephthalide (PDP) was chosen as the object of study being the representative electro-active polymer demonstrating induced electric conductivity. PDP is a carbocyclic polymer with high chemical and thermal stability, transparency in the visible spectrum and high mechanical strength [3, 4]. PDP has an amorphous structure with a degree of crystallinity not exceeding 15%. It is characterized by unusually high chemical resistance. The conditions for the selective production of PDP with a molecular weight of more than $(50-60) \times 10^3$ without the formation of a gel fraction have been found. A model image of the structural unit of the PDP polymer is shown in Fig. 1a. Polymers of this class are soluble in organic solvents and have exceptional film-forming properties [5, 6]. According to these results, continuous homogeneous films can be obtained by centrifugation from a solution in cyclohexanone on a metal surface with a thickness from several nanometers up to micrometers. High homogeneity and defect-free surface on nanoscopic scales have been repeatedly confirmed by various methods, including scanning tunneling and atomic force microscopy. In some cases, it was possible to observe regions with surface macromolecular (quasicrystalline) ordering [7].

The remarkable property of PDP is that, depending on the length of certain atomic bonds, its molecule can exist in several spatial configurations. Under normal conditions, PDP is a wide-gap dielectric material and is characterized by the following parameters: band gap ~ 4.3 eV, electronic work function ~ 4.2 eV, electron affinity ~ 2 eV, first ionization potential ~ 6.2 eV. However, in another

(metastable) state, e.g. induced by external electric field, the system is characterized by non-zero density of electronic states within the energy gap. The depth of such states increases if the system accepts an extra electron (Fig. 1b), thus indirectly enabling electric conductivity along the polymer chain [8].

The purpose of this work was to study this interesting phenomenon in a wide temperature range: from 4.2 K to room temperature.

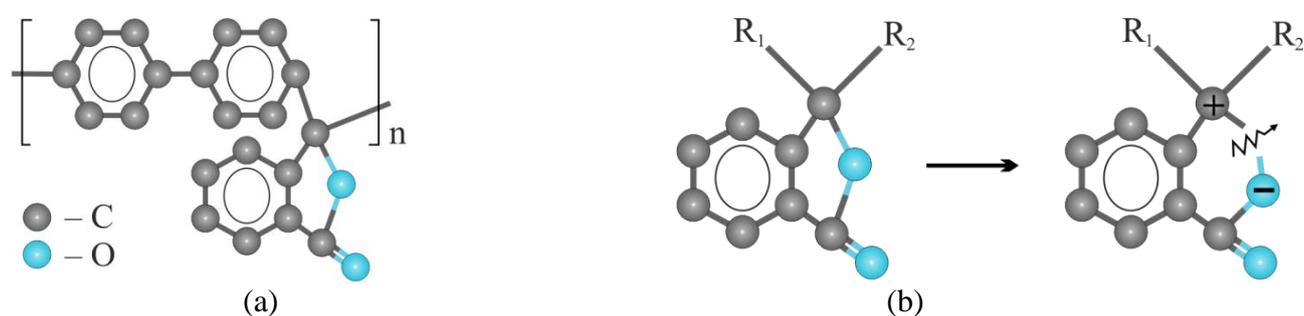


Figure 1: (a) Structural unit of polydiphenylenephthalide (PDP) molecule. (b) Schematics of C – O bond break leading to C⁺ and O⁻ ionization of the corresponding atoms, which enable effective charge transfer along the polymer chain [2].


Experimental


Layered Pb–PDP–Pb heterostructures were fabricated in a glove box in nitrogen atmosphere with minimum moisture and oxygen content without exposure to room atmosphere between cycles of formation of different layers. Glass or oxidized silicon were used as substrates. The substrates were preliminarily cleaned in ethanol and distilled water in ultrasonic bath. The surfaces were hydrophilized by treating the substrates with cyclohexanone immediately before applying the polymer solution. The electrodes consisted of two mutually perpendicular lead strips with a width of ~1 mm, between which the PDP polymer film was ‘sandwiched’ (Fig. 2a). Lead was chosen as fairly low-melting metal exhibiting superconducting properties. Formation of thin-film lead electrodes with thickness from 50

nm to 200 nm was carried out by thermal evaporation in vacuum. The critical temperature of bulk lead is $T_c(\text{Pb}_{3\text{D}})=7.2$ K. However, in the form of a thin film, the critical temperature of a superconductor can differ significantly from the tabulated value [9, 10]. In our samples, the critical temperature of lead electrodes varied from $7.8 \text{ K} < T_c(\text{Pb}_{\text{film}}) < 8.2 \text{ K}$. Submicron PDP films were prepared by centrifuging a polymer from a solution in cyclohexanone on a solid substrate. When preparing the solution, the polymer was first soaked in a small amount of solvent until complete dissolution, then the solvent was added in the required amount, and the solution was kept for another day in the dark. For fabrication of films of various thicknesses, solutions of polymers in cyclohexanone with concentrations of 0.1–15 wt % were used. The polymer solution of specified concentration was applied onto dielectric substrate fixed on a centrifuge holder. The rotation speed was typically 2000 rpm. The resulting polymer film was dried in air for about 45–60 minutes at room temperature. Then the final drying was carried out to remove solvent residues at a temperature of 150–200 °C for 45 minutes. Depending on concentration of the solutions, it was possible to obtain films of various thicknesses from several nm to several μm . The formation of films from dilute solutions occurs according to the mechanism of linear or loop adsorption, when macromolecules at the interface are completely or partially elongated. Also, film formation at such low concentrations strongly depends on the energy interaction of macromolecules with the substrate surface, which explains the weak dependence of the film thickness on the solution concentration. With an increase in concentration, associates of macromolecules are formed in the solution, and the influence of adhesion processes decreases, but the cohesive forces increase. In the entire thickness range from 3 nm to 1 μm , the films are solid, without significant defects and/or pin holes. The polymer films were studied by atomic force microscopy (AFM) using earlier described methodology [5]. The study of the film morphology showed that they are homogeneous, and within the entire thickness range from 3 nm to 1 μm the films are solid, without significant defects and/or pin holes. The observation confirms the good film-forming properties of the PDP polymer solutions. For example, Fig. 2b shows the topography of polymer film 0.1 wt. % on Si substrate. The plot at the

bottom demonstrates the variation of the structure along the line, depicted at the upper panel. The distance between the measuring lines is of the order of the polymer film thickness, which is just 3 nm.

After electric measurements, a number of heterostructures was sent for analysis by high resolution transmission electron microscopy and/or scanning electron microscopy. None of the studied samples showed a systematic ‘sticking’ of lead electrodes through the thickness of the polymer or formation of multiple metallic dendrites. However, a number of microphotographs shows some defects in the form of shortcuts (Fig. 2c). The origin of these artifacts is not entirely clear: they could be initially present in heterostructures, or they could have appeared during the preparation of a sample for electron microscopy.

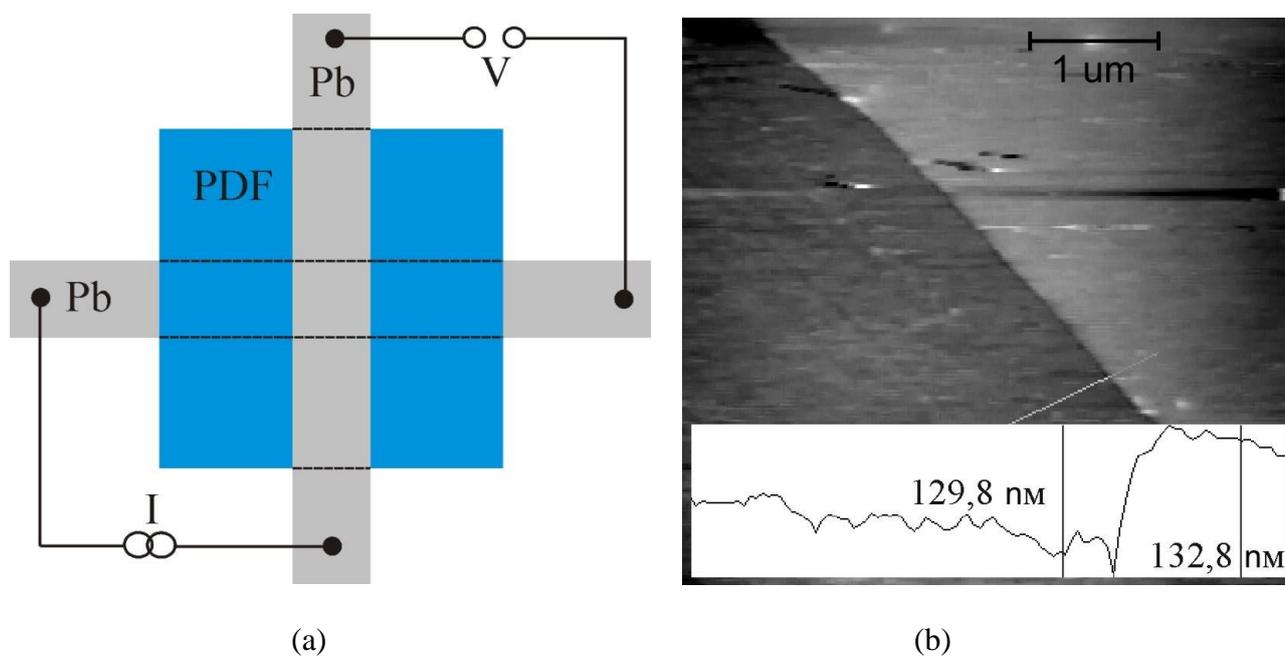

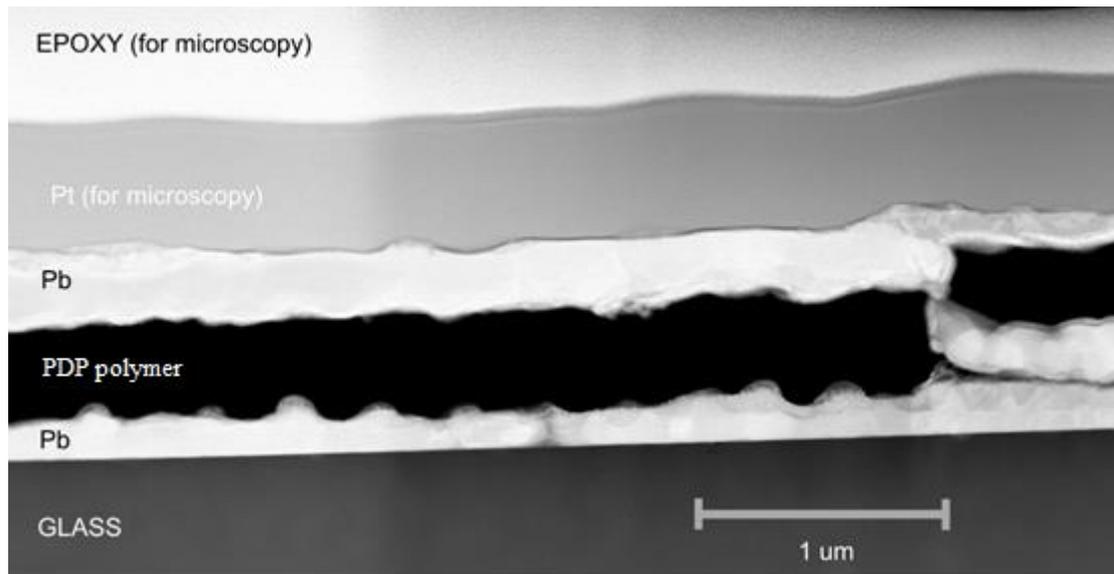

(c)

Figure 2: (a) Schematics of a Pb (grey) – PDP (blue) – Pb (grey) three layer heterostructure on insulating substrate (not indicated for simplicity). The layout enables electron transport measurements of the each lead strip and the whole sandwich itself. (b) Atomic force microscope scan of a PDP film 0.1 wt. % on Si substrate. The plot at the bottom illustrates the roughness of the surface along the indicated line. (c) Side view of a Pb-PDP-Pb structure on glass with solitary defect (lead shortcut) obtained by transmission electron microscopy.

Results and Discussion

The experiment was carried out in a four-contact configuration at direct or alternating currents. Both $R(T)$ and $V(I)$ dependences of the Pb-PDP-Pb sandwich could be measured, as shown in Fig. 2a, and the transport characteristics of each lead electrode separately. To measure differential characteristics $dI/dV(V)$, modulation technique and phase-sensitive lock-in detection were used. To suppress the negative effect of stray electromagnetic pickups, a multistage RLC filter system was used [11]. While $R(T)$ measurements at cryogenic temperatures, the current value from $0.1 \mu\text{A}$ to $100 \mu\text{A}$ was chosen so that its increase by an order of magnitude would not lead to a noticeable shift in the

temperature of the superconducting phase transition. All experiments were carried out in a ^4He direct pumped cryostat. The semiconducting thermosensors were calibrated by the ^4He vapor pressure and by the reference points of superconducting transitions in pure bulk superconductors (Al, In, Sn, Pb). The resulting absolute error in determining the temperature was ~ 10 mK, while the relative error was less than 1 mK. Repeated measurements of T_c of the same sample coincided with an accuracy of several mK. An analysis was made of the degradation of samples over time. The difference between two measurements of the same sample was 3 months, while the shift in the beginning of the phase transition was minimal $\delta T_c \approx 0.01$ K.

It has been established that in the measured Pb-PDP-Pb structure, the shape of the current-voltage characteristics strongly depends on temperature. At 300 K the I–V dependencies have a nonlinear character $j \sim kU^m$, typical for organic dielectrics. At temperatures ~ 77 K and below, the dependence $j = f(U)$ is also nonlinear, but is significantly different. In particular, as the voltage increases, there is the tendency for the current flowing through the heterostructure to saturate. Previously [2], it was found that at high temperatures, the mechanism of overcoming the barrier at the metal/polymer contact is satisfactorily described in terms of the injection current model limited by the space charge. At low temperatures, the tunneling mechanism is the predominant mechanism.

Fig. 3 shows the current voltage characteristics of Pb–PDP – Pb structures with different PDP film thicknesses. With increase of the polymer film thickness, the current decreases. Therefore they were measured over a wide voltage range. The shape of the I-V characteristics depends on the energy spectrum. Several regimes could be distinguished on the I-V plots: (a) ohmic mode at low voltages: thermally generated charge carriers prevail; (b) mode with a predominance of traps: trapped charge carriers in small traps limit the current; (c) the limit of trap filling: the quasi-Fermi level reaches the energy of the trap E_t , the traps are filled and there is a steep increase in current. It should be noted that in a circuit with finite load resistance the effect of electronic switching to a highly conductive state can

be observed (Fig. 3f). Such a bi-stable switching is often used in practice to create non-volatile memory elements.

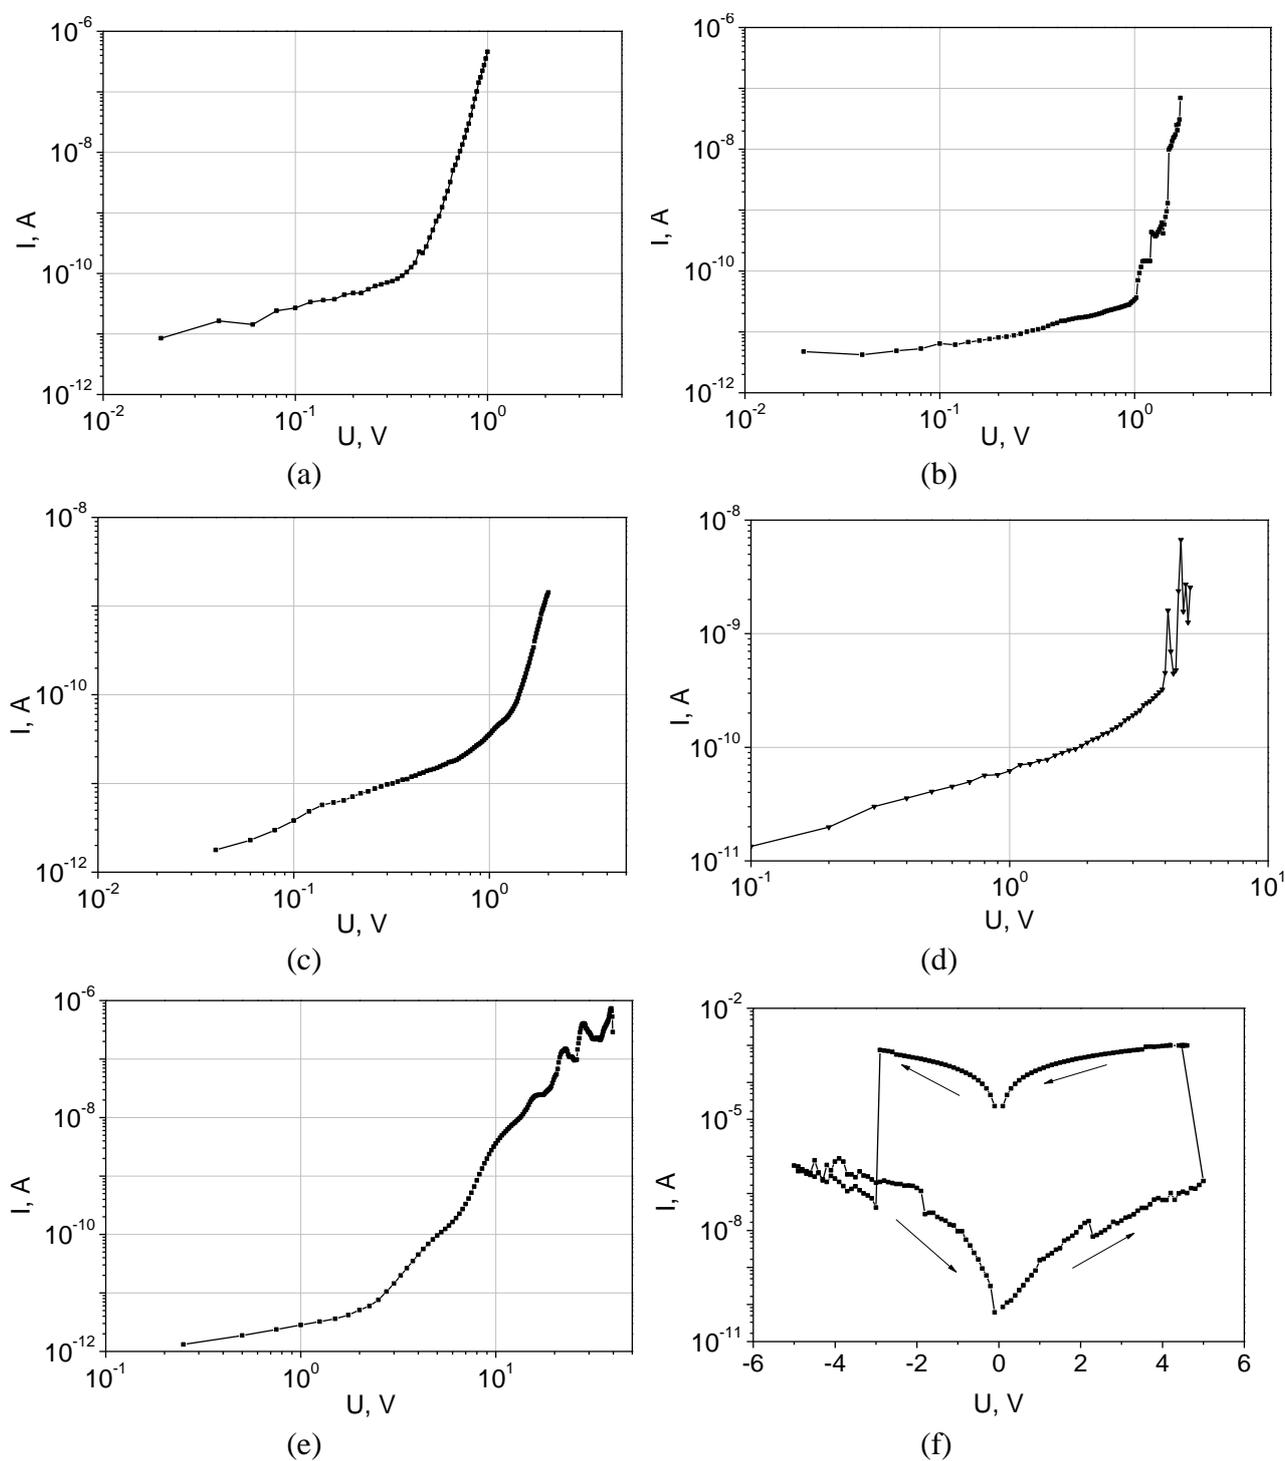


Figure 3: Current voltage characteristics, measured at room temperature, of several Pb – PDP – Pb sandwiches with different thicknesses of the polymer film: (a) 10 nm, (b) 25 nm, (c) 45 nm, (d) 150

nm, (e) 360 nm. (f) is the same structure as (c) and with 2 kOhm load resistance in the electric circuit. (f) demonstrates the switching phenomenon of the thin PDP film from insulating to metal state.

Presented in Fig. 3 I-V characteristics do not contradict the presented above model considerations. In this regard, to analyze the I-V at 300 K, one can apply the formalism of the theory of injection currents, which makes it possible to estimate the concentration of intrinsic charge carriers (n_0) and their minimum mobility (μ) [12]:

$$n_0 = \frac{\varepsilon\varepsilon_0 U_n}{eL^2}, \quad (1)$$

$$\mu = \frac{jL^3}{\varepsilon\varepsilon_0 U_n^2}, \quad (2)$$

where, j is the current density, L is the distance between the electrodes, U_n is the voltage corresponding to the transition point from linear to parabolic dependency of the I-V's, n_0 is the equilibrium concentration of charge carriers, ε and ε_0 dielectric constants of the polymer and vacuum, respectively, and μ is the maximum mobility of charge carriers.

According to this model, the ohmic behavior of the I-V characteristics at low voltages is due to intrinsic charge carriers. If, however, the concentration of injected carriers begins to exceed the concentration of intrinsic carriers, then the transition to sublinear regime is observed. The corresponding estimations give the following values $n_0 = 10^{21} - 10^{23} \text{ m}^{-3}$, $\mu = 10^{-15} - 10^{-17} \text{ m}^2/\text{Vs}$.

The analysis of the I-V characteristics within the framework of Schottky barrier formation makes it possible to estimate the height of potential barriers at the metal/polymer interfaces utilizing the Richardson expression [12]:

$$\varphi = \frac{kT}{e} \ln \left(\frac{AA^* T^2}{I_s} \right), \quad (3)$$


where T is the temperature, k is the Boltzmann constant, q is the electron charge, A is the contact area, A^* is the Richardson constant, I_s is the saturation current. To proceed, it is important to determine the saturation current using e.g. the semi-logarithmic dependence of the current on applied voltage. This

is the so-called current at zero voltage. In addition it is necessary to take into account the non-ideality coefficient of the barrier. We chose the value of the latter from previous measurements. As the result, the value of the potential barrier calculated using expression (3) is equal to 0.7. As expected, the transport characteristics of thin-film lead electrodes demonstrated the metallic behavior: in normal state, the resistance of the films decreased linearly with decreasing temperature, and the I–V characteristics exhibit ohmic behavior. At temperatures of the order of $T_c(\text{Pb}_{\text{film}}) \approx 8$ K, a sharp superconducting transition was observed.

Perhaps the most interesting are the results of transport measurements of Pb-PDP-Pb sandwiches at temperatures below the critical temperature of the superconducting transition of lead electrodes. In a number of samples, with a polymer film thickness of less than 350 nm, features are observed that unambiguously indicate the presence of a superconducting state: a sharp drop in resistance to instrumental zero ~ 5 nV (Fig. 4 a) and presence of supercurrent in the I-V's (Fig. 4 b-c-d). A trivial explanation may be the occurrence of shortcuts between the lead plates: either macroscopic 'pinholes' or formation of multiple thin dendrites. The second possibility seems unlikely: neither the previous studies, nor the selective microscopic analysis of several samples by scanning and transmission electron microscopy revealed signs of the presence of dendrites. While the side view microphotographs made by high-resolution transmission electron microscopy occasionally reveal some macroscopic features such as lead electrode shortcuts through the polymer film (Fig. 2c). These defects are episodic, and their character does not resemble the 'melting through' of the PDP film during the thermal deposition of lead. Moreover, the PDP decomposition starts at 440 °C, which is significantly higher than the melting point of lead, 327 °C. Moreover, it cannot be ruled out that such defects as 'collapse' of lead electrodes (Fig. 2c) are not intrinsic, and could have appeared only during the process of sample preparation for transmission microscopy. The sufficiently high critical current (Fig. 4 b-d) also indicates the large area of the conductive channel, which does not correspond to the scenario of the occurrence of single point short circuits. The I-V dependencies of the Pb-PDP-Pb

sandwiches above the superconducting temperature of the lead electrodes are essentially non-ohmic (Fig. 3), which supports the claim about the absence of trivial metal-to-metal shortcuts.

The second alternative explanation of the dependencies in Fig. 4 may be the Josephson effect: the flow of supercurrent between two superconductors separated by a dielectric barrier. However, the correlation of the order parameters of two spatially separated superconductors is a subtle quantum mechanical effect, which in all practical cases is observed at dielectric thicknesses of the order of several nm, while in our case superconductivity in Pb-PDP-Pb sandwiches manifests itself at polymer thicknesses up to 350 nm. Hence, it can be assumed that the dependencies in Fig. 4 can be explained by the effect of induced superconductivity in a thin film of conducting polymer enclosed between two massive superconductors (lead). The substantiation of this assertion requires further verification. In the near future, experiments are planned on planar heterostructures, where superconductivity, if observed, cannot be explained by trivial metallic shortcuts.

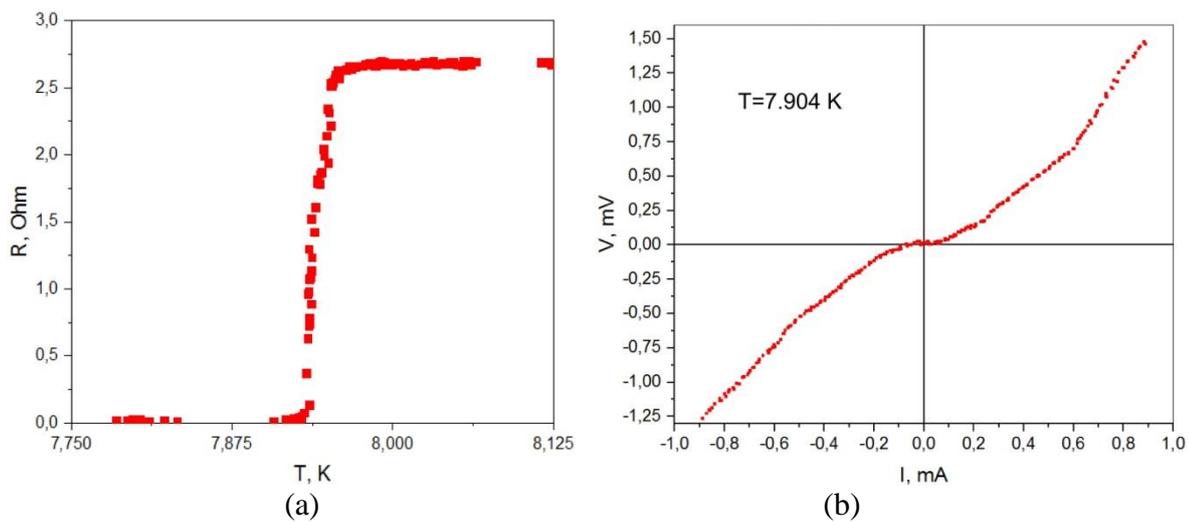

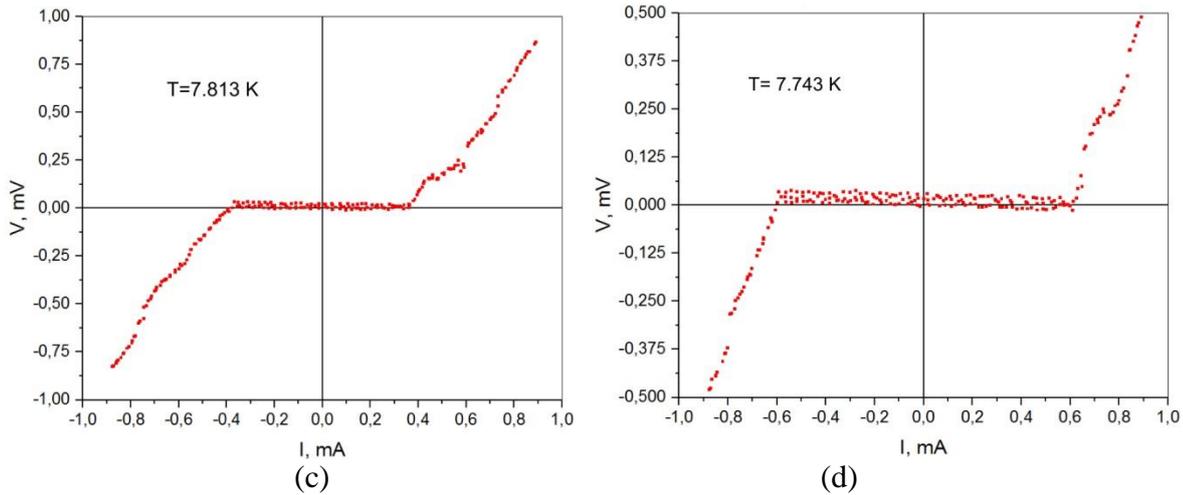


Figure 4: Sandwich structure Pb-PDP-Pb-0,4-GLASS. (a) Resistance vs. temperature $R(T)$ dependence. (b)-(c)-(d) Voltage vs. current $V(I)$ characteristics measured at various temperatures.

Summary

$R(T)$, $V(I)$ and $dV/dI(V)$ dependences of thin-film layered structures lead – PDP – lead were experimentally studied in a wide temperature range. At sufficiently high temperatures, the I - V dependences are satisfactorily described in terms of the currents injection model limited by the space charge. At temperatures below ~ 8 K, a number of samples exhibit features that can be explained by the effect of induced superconductivity in a thin film of a conducting polymer enclosed between two massive superconductors (lead).

Acknowledgements

The work was supported by the Mirror Lab project between HSE University and Bashkir state pedagogic University. The samples were fabricated using equipment of the Center for Collective Use "Agidel" of the UFRC RAS. The activity of A.S.G. was supported by the Basic Research program of HSE University.

References

1. A.N. Lachinov, V.M. Kornilov, T.G. Zagurenko and A.Yu. Zherebov, JETP 102(4), 640 (2006).
2. A.N. Lachinov, N.V. Vorob'eva, Physics - Uspekhi 49(12), 1223 (2006).
3. S.N. Salazkin et. al., Polymer Science A, 29, 1431 (1987).
4. S.N. Salazkin, Polymer Science B 46, 1244 (2004).
5. D.D. Karamov, V.M. Kornilov, A.N. Lachinov, V.A. Kraikin and I.A. Ionova, Technical Physics, 61(7), 1085 (2016).
6. A. N. Lachinov, A.R.Tameev, A.R.Yusupov and A.V.Vannikov, Electrochemistry 48(3), 347 (2012).
7. V. M. Kornilov, A. N. Lachinov, JETP Letters 61(6), 520 (1995).
8. D. G. Zykov, Y. V. Vasil'ev, V. S. Fal'ko, JETP Lett. 64, 439 (1996).
9. K. Yu. Arutyunov, et. al., Phys. Status Solidi RRL 13, 1800317 (2019).
10. K. Yu. Arutyunov, et. al, Phys. Sol. St. 61(9), 1559 (2019).
11. V. V. Zavyalov, S. A. Chernyaev, K. V. Shein, A.G. Shukaleva and K.Yu. Arutyunov, Journal of Physics: Conference series 969, 012086 (2018).
12. A. R.Yusupov, R.M. Gadiev, A.N. Lachinov, V.M. Kornilov, L.R. Kalimullina, A.F. Galiev, M. Kian and S.N. Salazkin , Synthetic Metals 274, 116733 (2021).